



VOLUME 7 ISSUE 1-2 June 2016 ISSN 1986-602X
The Republic of Srpska, Bosnia and Herzegovina EISSN 1986-6038

UDC 614

A Multidisciplinary Journal of Food Science,
Environmental Science and Public Health

APEIRON
ΑΠΕΙΡΟΝ



VOLUME 7
ISSUE 1-2

Quality of Life

(Banja Luka)

A Multidisciplinary Journal of Food Science, Environmental Science and Public Health

Izdavač/Published by Panevropski univerzitet "Apeiron" Banja Luka/ Pan-European University "Apeiron" Banja Luka
Urednik izdavača/Editor of University Publications Aleksandra Vidović, Bosnia and Herzegovina

Editor-in-Chief

Radoslav Grujić (Bosnia and Herzegovina)

Assistant Editors

Bogoljub AntoniĆ (Sanitary inspection and control)

Drago Nedić (Public health engineering)

Radoslav Grujić (Food science and technology, Nutrition)

Milorad Balaban (Environmental and Public Health)

International Editorial Board

Cantalejo Maria-Jesus (Spain)
Đonlagić Nusreta (Bosnia and Herzegovina)
Giuseppe Enne (Italy)
Grujić Radoslav (Bosnia and Herzegovina)
Grujić Slavica (Bosnia and Herzegovina)
Olga Martín-Belloso (Spain)
Miletić Predrag (Bosnia and Herzegovina)
Minkov Ivan (Bulgaria)
Murković Michael (Austria)
Nedić Drago (Bosnia and Herzegovina)
Radovanović Radomir (Serbia)
Rajković Andrea (Belgium)
Srebenkoska Vineta (Macedonia)
Vasiljević Todor (Australia)
Zavargo Zoltan (Serbia)

Editorial council

Aleksić Siniša (Bosnia and Herzegovina)
Andretta Dario (Italy)
Ateljević Jovo (United Kingdom)
Avramović Ž. Zoran (Serbia)
Balaban Milorad (Bosnia and Herzegovina)
Čakić Milorad (Serbia)
Đurić Zdenka (Serbia)
Golubović Srbojub (Bosnia and Herzegovina)
Grujić Radoslav (Bosnia and Herzegovina)
Jašić Midhat (Bosnia and Herzegovina)
Kozomara Risto (Bosnia and Herzegovina)
Radić Gordana (Bosnia and Herzegovina)
Uremović Darko (Bosnia and Herzegovina)
Vidović Aleksandra (Bosnia and Herzegovina)

Editorial Office

Quality of Life

Pan-European University Apeiron
Pere Krece 13, 78 000 Banja Luka, B&H
Tel: +387 51 247 910
Mob: +387 65 141 619
Fax: +387 51 247 921
e-mail: info@qol-au.com,
sekretar@qol-au.com,
redakcija@qol-au.com
URL: <http://www.qol-au.com>

Secretary

Igor Grujić

Language Editor

(English, Serbian)

Technical

Editor/Layout

Sretko Bojić

Web design

Miloš Pašić

Printed by

Artprint, Banja Luka
Printed in 300 copies

Aim and Scope

Quality of Life publishes original research papers and reviews and aims to provide a forum for the rapid dissemination of significant novel research in the various disciplines encompassing the Science and technology of food, Public health engineering, Sanitary inspection and control, Environmental and public health. Topics covered by the journal include:

- Dietetics; Nutrition principles applied to foods
- Food Technology; Production and preservation of foodstuffs; Food preservation technique
- Industrial microbiology; Science and technique of applied microbiology; Applied mycology
- Public Health, environment and hygiene
- Hygiene of air, water, soil; Pollution and its control
- Water; Sanitation; Water treatment
- Sewage; Treatment, disposal, utilization of sewage
- Urban hygiene; Wastes; Refuse; Rubbish; Garbage; Collection and disposal of town wastes
- Measures against industrial and other nuisances
- Occupational health hazards; Occupational health and hygiene
- Ecology; Environmental engineering, sustainability and health
- Related topics

UDC 614

Quality of Life is registered with the Ministry of Science and Technology of the Republic of Srpska by serial registration code 07.030-053-160-4/10, date 03.03.2010.

Quality of Life (ISSN 1986-602X) is an international journal published four times a year.

Indexed in: LICENSE AGREEMENT, 3.22.12. EBSCO Publishing Inc., Current Abstracts

 ebscobase.com

 indexcopernicus.com

 citefactor.org/contact

 scholar.google.com

 doisrpska.nub.rs

 crossref.org

 road.issn.org

 cosmosimpactfactor.com

REMOVAL OF Ni(II) IONS FROM AQUEOUS SOLUTIONS BY NANOPOROUS MATERIAL

SHABAN JAKUPI¹, KATERINA ATKOVSKA², KIRIL LISICHKOV^{2*}, MIRJANA GOLOMEOVA¹,
MIRKO MARINKOVSKI², STEFAN KUVENDZIEV²

¹Faculty of Natural and Technical Sciences, University "Goce Delchev", Stip, Macedonia

²Faculty of Technology and Metallurgy, University "Ss. Cyril and Methodius", Rugjer Boskovic 16, Skopje, Macedonia
klisickov@yahoo.com

Abstract: The novel trends in green separation processes impose the need for application of natural, low-cost and high-efficiency selective adsorbents, such as natural zeolite, within the processes for the treatment of drinking water supplies. Lately, nano-porous inorganic sorbents represent an ongoing trend for elimination of heavy metals from water resources. In the frame of this work, the nanoporous material, clinoptilolite, was applied for removal of Ni(II) ions from water resource. The experimental results were obtained in a laboratory scale batch glass reactor with continuous stirring at 400 rpm. The effects of the mass of the nano-porous adsorbent and the initial pH of the solution were studied to optimize the conditions for maximal removal of Ni(II) ions. MATLAB/Curve Fitting Toolbox was implemented to determine the adequate adsorption isotherm as well as to optimize the equilibrium state of the investigated system.

Keywords: natural zeolite - clinoptilolite, Ni(II) ions, adsorption, nano-porous sorbent, equilibrium study

Introduction

The rapid industrial development and urbanization have intensified environmental pollution and caused deterioration of eco-systems by accumulation of many pollutants, especially heavy metals. Most of the heavy metals are toxic and their ions are not biodegradable, hence they are significant environmental pollutants. Therefore, the removal of the heavy metal ions from water and wastewater is very important for environmental protection, and thus the public health.

The methods used for removal of heavy metals from water and wastewater include chemical precipitation, ion exchange, solvent extraction, electrolysis, membrane processes, adsorption (Fu and Wang 2011, Vindoh, Padmavathi and Sangeetha 2011, Bakalar, Bugel and Gajdosova 2009, Rahul 2013, Lokendra and Mukesh 2013). Among all the approaches proposed, adsorption is one of the most popular method and it is considered as an effective, efficient and economic method for wastewater purification and it is widely used in effluent treatment processes. Various materials such as natural and synthetic zeolites (Zoran et al., 2014, Anielak and Schmidt 2011, Shaheen, Derbalahand Moghanm 2012, Wang and Peng 2010), clay minerals (Ghormi, Lahsini, Laajeb and Addaou 2013), activated carbon (Kouakou, Ello, Yapo and Trokourey 2013), biosorbents (Miretzky and Cirelli 2009), have been used as adsorbents for the removal of heavy metals from water and wastewater.

The zeolites are nanoporous minerals, characterized by specific structure of the frame and regulated pore geometry. The zeolites have high ion exchange capacity and selective adsorption capacity, thermal and mechanical stability (Passaglia and Sheppard 2001). There are natural and synthetic zeolites. The zeolite - clinoptilolite is natural zeolite. Natural zeolites are obtained by performing the excavation. Zeolites consist of SiO₄ and AlO₄ tetrahedrons, connected in skeletal structure. The aluminosilicate structure has negative charge that attracts the inside positive cations. The zeolites in their structure have large cavities where cations like K, Na, Ba or Ca, large molecules of organic compounds, cationic groups of ammonia, carbonate and nitrate ions, and ions of heavy metals can penetrate and can be adsorbed.

A great deal of interest in the research for the removal of heavy metals from aqueous solutions has been focused on the use of zeolites as adsorbents. High ion-exchange capacity, high specific surface area and their relatively low cost, make them attractive adsorbents for elimination of heavy metals from water systems.

Many research works have used natural zeolite as an appropriate adsorbent for heavy metals removal (Ghasemi, Gafar, Mousavi and Dehghan 2012, Sabry, Aly, and Farahat 2012, Salunkhe and Raut 2012). The aim of this article is to investigate the adsorption availability of natural zeolite - clinoptilolite to remove Ni(II) ions from aqueous solutions.

Materials and Methods

Adsorbent

The natural zeolite (clinoptilolite) used as adsorbent for Ni(II) ions removal from aqueous solutions, was taken from Kardzali, Bulgaria.

Reagents and Chemicals

Standard solution of nickel nitrate, $\text{Ni}(\text{NO}_3)_2$ (1 g/dm³), hydrochloric acid, HCl (0.1 M), sodium hydroxide, NaOH (0.1 M), natural nano-porous zeolite. All the reagents and chemicals used in the experiment were analytical grade.

Adsorption experiment

Batch adsorption experiments were performed to obtain equilibrium data. Standard solution of $\text{Ni}(\text{NO}_3)_2$ with concentration of 1 g/l was used to prepare solution with different initial Ni(II) concentration (350-650 µg/l). The effect of the amount of zeolite and the influence of pH were investigated. 0.25, 0.5 and 1 g/l of the applied zeolite were placed at three different beakers, then 2 l of the Ni(II) solution with the desired concentration were added in each beaker. The mixture of natural zeolite and Ni(II) solution with 450 µg/l concentration and pH = 6.0, were stirred using magnetic stirrer at 400 rpm, at constant room temperature for 5 h, sufficient time to reach equilibrium. The influence of pH was conducted with adsorbent amount of 0.3 g/l at 2 l of the solution with 450 µg/l concentration of nickel ions and at the same stirring conditions as mentioned before. The initial pH of 4, 6 and 8 were adjusted by adding either 0.1 M HCl or 0.1 M NaOH solutions.

The samples were taken at particular time, filtered and the remaining concentrations of Ni(II) ions in the filtrate were determined using atomic absorption spectrophotometer, AAS Perkin Elmer model AA700.

Experimental data were processed by the three most commonly used isotherms: Langmuir, Langmuir-Freundlich and Redlich - Peterson isotherm, by using MATLAB/ Curve Fitting Toolbox.

Results and Discussion

Material characterization

The clinoptilolite used for experimental analysis is in the form of granules and the particle size range of the natural zeolites used in this study was 0.8 to 2.5 mm.

The results of chemical composition of clinoptilolite determined by classical silicate chemical analysis are presented in Table 1.

Table 1. Chemical composition of clinoptilolite

Oxides	SiO ₂	Al ₂ O ₃	CaO	Fe ₂ O ₃	MgO	Na ₂ O	K ₂ O	TiO ₂	LOI
wt. %	72.0	12.0	3.7	1.9	1.2	0.5	3.8	0.04	4.86

The monolayer capacity and specific surface of clinoptilolite are evaluated from data of equilibrium adsorption of water vapor at 298K, using linear form of Langmuir equation. The values of the parameters of the Langmuir equation, monolayer capacity, n_m^a and constant b , and the specific surface, a_s are $4,2 \cdot 10^{-3}$ mol/g, 0,56, and 268 m²/g, respectively (Katerina, Blagica, Biljana and Vesna2014). The high value of specific surface of clinoptilolite enables it to be used as adsorbent for heavy metals removal from industrial wastewaters (Milicevic et al., 2013).

Adsorption studies

The adsorbed amount of metal ion q [μg/g], was calculated using the following equation expressed as:

$$q = \frac{(C_0 - C_t)V}{m} \quad (1)$$


where C_0 is initial concentration of the Ni(II) ions [μg/l], C_t is concentration of Ni(II) ions [μg/l] at particular time of adsorption, V is volume of the solution [l] and m is mass of the adsorbent [g].

The percentage of removal of Ni(II) ions was determined using the Equation 2:

$$\%R = \frac{C_0 - C_e}{C_0} \cdot 100 \quad (2)$$

where C_e is equilibrium concentration of Ni(II) ions [μg/l].

Effect of amount of adsorbent

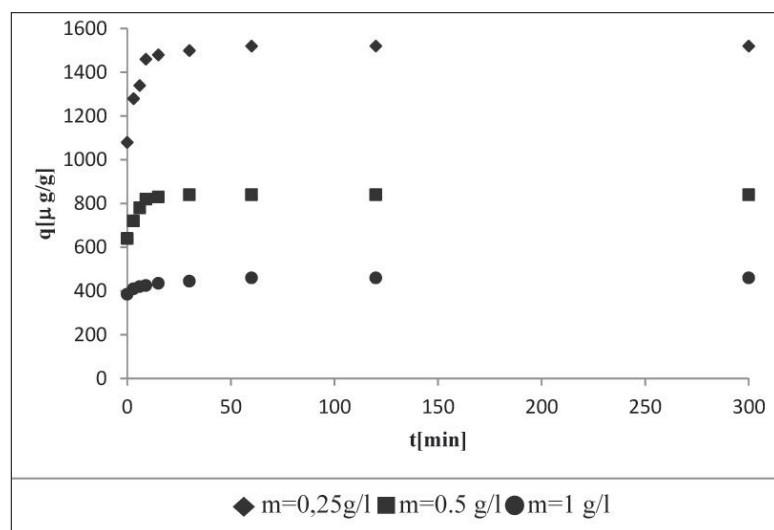

The effect of the dosage of the natural zeolite on the removal of Ni(II) is given in Figure 1 and Figure 2. The Figure 1 shows that the amount of Ni(II) adsorbed per unit mass, q , decreases with increase of the adsorbent amount. It was found that, when adsorbent dose increases the total surface area decreases, this increase in diffusion path length, could be explained as a result of aggregation of zeolite particles.

Figure 1. Experimental equilibrium data of the system Ni(II) - natural zeolite

However, the percentage of removal of Ni(II) increases by increasing the adsorbent amount. The removal percentages are 80, 89 and 96 % for adsorbent dosage of 0.25, 0.5 and 1 g/l, respectively, as it is shown at Figure 2. This is to be expected because, for a fixed initial concentration of the solution, increasing adsorbent amount provides greater surface area or adsorption sites.

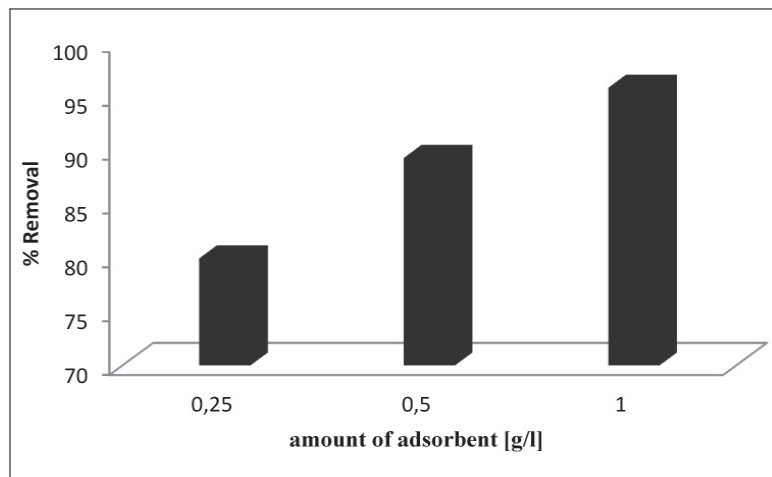


Figure 2. Function of Ni(II) removal from amount of adsorbent

Effect of pH

The pH of the solution is an important variable which controls the adsorption of the metal ions at the solid-water interface. The influence of pH on the adsorption of Ni(II) ions onto natural zeolite was examined at pH 4, 6 and 8. The general trend in the amount adsorbed (q) as well as the

percentage of removal with increase in pH is positive. Figure 3 represents the trend in the amount of Ni(II) ions adsorbed in respect of time at different pH of the solution. It is observed that adsorption increases with increase in pH value of Ni(II) solution.

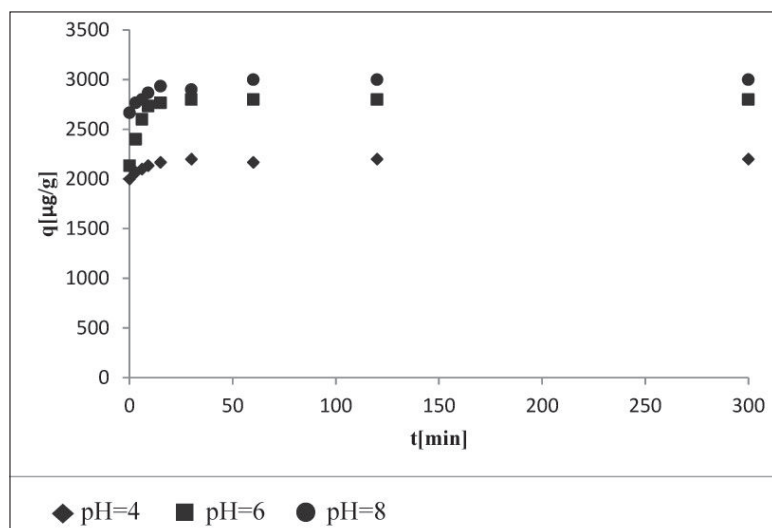


Figure 3. Experimental equilibrium data for the system Ni(II) - natural zeolite

The percentage of removal of Ni(II) ions, also increases by increasing the pH of the solution, Figure 4. The removal percentages are 69, 89 and 94% for pH 4, 6 and 8, respectively. Similar studies were in agreement with this findings (Ismail, Zhang and Adnan, 2012).

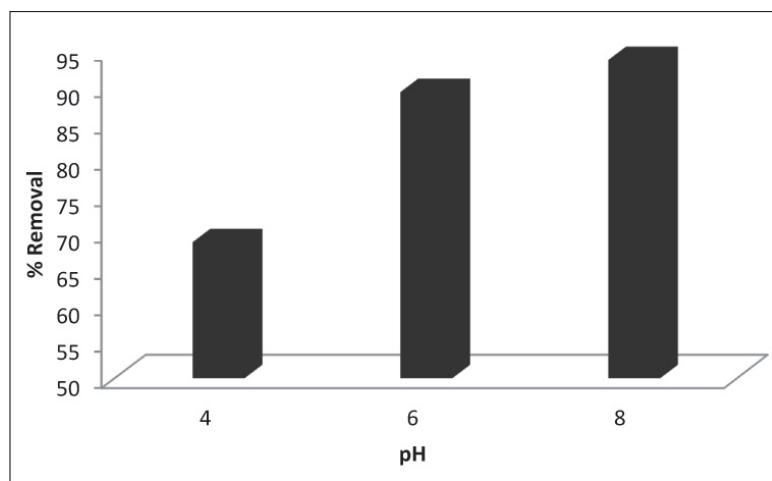


Figure 4. Function of Ni(II) removal from pH of the solution

Generally, the acidification of the aqueous phase leads to an increase of proton occupying the active sites in the adsorbent structure (Singh, Verma, Sambi and Sharma 2008). At low pH, the number of H^+ ions exceeds several times than metal ions and the Ni(II) ions can hardly compete with H^+ ions for the binding sites on the zeolite. When an increase of pH, the

concentration of H^+ ions decreases and there are more active sites of clinoptilolite available for metal ions. Hence, pH 6 was chosen as the optimum pH value for this adsorption process.

Adsorption isotherms

Adsorption isotherms are important for adsorption processes research. Figure 5 shows the plot of adsorbed amount of Ni(II) ions at equilibrium versus equilibrium concentrations.

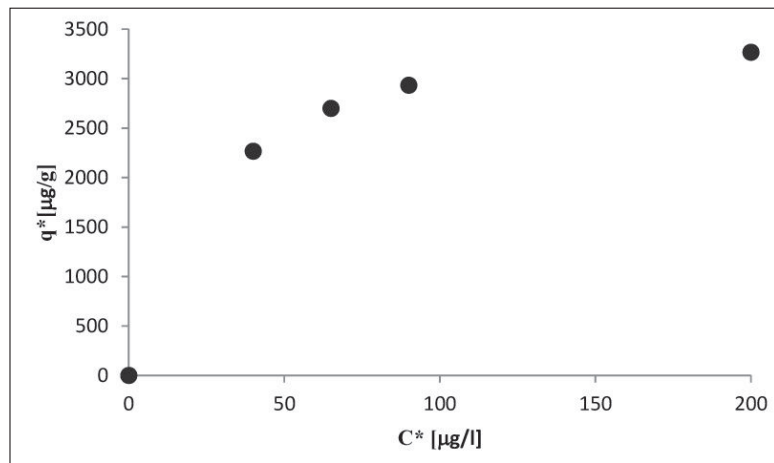


Figure 5. Experimental adsorption isotherm for the system Ni(II) ions - natural zeolite

Experimental data were processed by the three most commonly used isotherms: Langmuir equation (Equation. 3), Langmuir-Freundlich (Equation 4) and Ridlich - Peterson (Equation 5), by using MATLAB/Curve Fitting Toolbox. The correct choice of the equilibrium isotherm is an important segment for determining the maximal capacity of the adsorbent for

the investigated adsorbate, and for modeling the kinetics and dynamics of adsorption.

$$q^* = \frac{q_m \cdot K_L \cdot C^*}{1 + K_L \cdot C^*} \quad (3)$$

$$q^* = \frac{q_m \cdot K_C \cdot C^{*1/n}}{1 + K_C \cdot C^{*1/n}} \quad (4)$$

$$q^* = \frac{K_{RP} \cdot C^*}{1 + A \cdot C^{*\beta}} \quad (5)$$

where, q_m [μg/g], K_C [l/μg]^{1/n}, K_L [l/μg] and n are parameters of Langmuir and Langmuir - Freundlich's isotherms, K_{RP} [l/μg], A [l/μg]^b and b are parameters of Ridlich - Peterson's isotherm.

The modeling of the experimental data for the investigated system applying Langmuir, Langmuir - Freundlich and Ridlich - Peterson models are given in Figure 6.

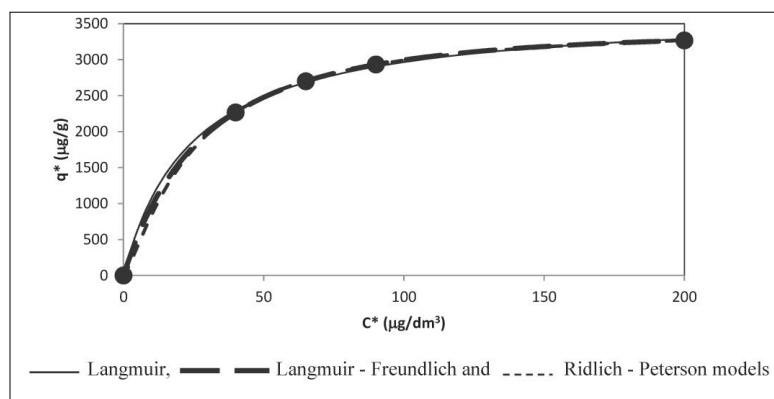


Figure 6. Modeling of the experimental data for the system Ni(II) ions - natural zeolite using

Table 2 contains the data of model parameters of the applied adsorption isotherms for Ni(II) ions adsorption on natural zeolite.

Table 2. Model parameters of the applied adsorption isotherms

	Langmuir	Langmuir-Freundlich	Ridlich-Peterson
q_m [μg/g]	3687.03	3513.1	
K_L [l/μg]	0.04109		
K_C [l/μg] ^{1/n}		0.01688	
n		0.7862	
A [l/g]			0.02106
K_{RP} [l/μg] ^{1/n}			120.3
b			1.078
R ²	0.9995	0.9999	0.9999

Satisfactory values of the maximal adsorption capacities of natural zeolite for Ni(II) removal were obtained by Langmuir and Langmuir - Freundlich isotherms and are 3687 and 3513 μg/g, respectively.

The high values of coefficients of correlation reveal that experimental results correspond well to the three used adsorption isotherm models.

Conclusion

In this study, the adsorption of Ni(II) ions on natural zeolite - clinoptilolite, was investigated. Chemical analysis showed that SiO₂ is major component in the clinoptilolite. This nanoporous material has high specific surface area of 268 m²/g. Batch experiments were conducted and showed that the adsorption of Ni(II) on natural zeolite is dependent of the adsorbent dosage and pH dependent. The Langmuir, Langmuir - Freundlich and Ridlich - Peterson isotherms were applied to study equilibrium data and all models indicate good correspondence to the experimental results.

It can be concluded that natural zeolite - clinoptilolite, considered in this work appears to be promising adsorbent with acceptable adsorption capacity for removal of nickel ions from aqueous solutions.

References

- Anielak, A. M. & Schmidt, R. (2011). Sorption of lead and cadmium cations on natural and manganese-modified zeolite. *Polish Journal of Environmental Studies*, 20(1), 43
- Bakalar, T., Bugel, M., Gajdosova, L. (2009). Heavy metal removal using reverse osmosis. *Acta Mont. Slov.* 14(3), 250-253
- Fu, F. & Wang, Q. (2011). Removal of heavy metal ions from wastewater: A review. *Journal of Environmental Management*, 92 (3), 407-418
- Ghasemi-Fasaee, R., Gafari-Haghighi, M., Mousavi, S. M. & Dehghan M. (2012). Sorption characteristics of heavy metals onto natural zeolite of clinoptilolite type. *International Research Journal of Applied and Basic Sciences*, 3(10), 2079-2084
- Ghormi, F., Lahsini, A., Laajeb, A. & Addaou, A. (2013). The removal of heavy metal ions (copper, zinc, nickel and cobalt) by natural bentonite. *Larhyss Journal*, 12, 37-54
- Ismail, M. H. S., Zhang, X. T. & Adnan S. N. (2012). Application of clinoptilolite in removal of nickel (II) in plating wastewater. *World Applied Sciences Journal*, 18(5), 659-664
- Katerina, A., Blagica, C., Biljana A. & Vesna M. (2014). Adsorption properties of natural zeolite - clinoptilolite. In *Proceedings of the VI International Conference Ecology of Urban Areas*, (pp. 303-306). Zrenjanin, Srbija
- Kouakou, U., Ello, A. S., Yapo J. A. & Trokourey, A. (2013). Adsorption of iron and zinc on commercial activated carbon. *Journal of Environmental Chemistry and Ecotoxicology*, 5(6), 168-171
- Lokendra, S. T. & Mukesh, P. (2013). Adsorption of heavy metal (Cu²⁺, Ni²⁺ and Zn²⁺) from synthetic waste water by tea waste adsorbent. *International Journal of Chemical and Physical Sciences*, 2(6), 6-19
- Milicevic, S., Milosevic, V., Povrenovic, D., Stojanovic, J., Martinovic, S., & Babic, B. (2013). Removal of heavy metals from aqueous solution using natural and Fe(III) oxyhydroxide clinoptilolite. *Clays and Clay Minerals*, 61, 231 - 257
- Miretzky, P. & Cirreli, A. F. (2009). Hg(II) removal from water by chitosan and chitosan derivatives: A review. *Journal of Hazardous Materials*, 167, 10-23

- Passaglia, A. & Sheppard, R. A. (2001). Crystal chemistry of zeolites. In Bish, D. L., Ming, D. W. (eds.). Natural zeolites: Occurrence, properties, application, Reviews in mineralogy and geochemistry. The Mineralogical Society of America, Washington DC
- Rahul, K. J.(2013). Application of electro-dialysis (ED) to remove divalent metals ions from wastewater. International Journal of Chemical Sciences and Application, 4(1), 68-72
- Sabry, M. S., Aly, S. D. and Farahat, S. M. (2012). Removal of heavy metals from aqueous solution by zeolite in competitive sorption system. International Journal of Environmental Science and Development, 3(4): 362-367
- Salunkhe, B. and Raut, S. J. (2012). Removal of heavy metal Ni(II) and Cr(VI) from aqueous solution by scolecite natural zeolite. International Journal of Chemical Sciences, 10(2): 1133-1148
- Shaheen, S. M., Derbalah, A. S. & Moghanm, F. S. Removal of heavy metals from aqueous solutions by zeolite in competitive sorption system. International Journal of Environmental Science Development, 3(4), 362-367
- Singh, S., Verma, L. K., Sambi, S. S. & Sharma, S. K. (2008). Adsorption behavior of Ni(II) from water onto zeolite: Kinetics and equilibrium studies. In the Proceedings of the World Congress on Engineering and Computer Science, (pp. 112-117)
- Vindoh, R., Padmavathi, R. & Sangeetha, D. (2011). Separation of heavy metals from water samples using anion exchange polymers by adsorption process. Desalination, 267(2), 267-276
- Wang, S. & Peng, Y. (2010). Natural zeolites as effective adsorbents in water and wastewater treatment. Chemical Engineering Journal, 156, 11-24
- Zoran, B., Kiril, L., Mirko, M., Stefan, K., Dejan, D. & Kostadin N. (2014). Equilibrium study for adsorption of arsenates and arsenates from aqueous solutions by application of modified natural inorganic materials. Quality of Life, 2(1-2), 46-52

Recived: 28.04.2016

Accepted: 20.05.2016