

## Book Chapter

# Effect of Thermal Treatment of Clayey Diatomite at Temperature Range 800-1200°C

Arianit A Reka<sup>1\*</sup>, Blagoj Pavlovski<sup>2</sup>, Egzon Ademi<sup>1</sup>, Ahmed Jashari<sup>1</sup>, Blazo Boev<sup>3</sup>, Ivan Boev<sup>3</sup> and Petre Makreski<sup>4</sup>

<sup>1</sup>Faculty of Natural Sciences and Mathematics, University of Tetovo, Republic of Macedonia

<sup>2</sup>Faculty of Technology and Metallurgy, Ss. Cyril and Methodius University, Republic of Macedonia

<sup>3</sup>Faculty of Natural and Technical Sciences, “Goce Delčev” University in Štip, Republic of Macedonia

<sup>4</sup>Institute of Chemistry, Faculty of Natural Sciences and Mathematics, Ss. Cyril and Methodius University, Republic of Macedonia

**\*Corresponding Author:** Arianit A Reka, Faculty of Natural Sciences and Mathematics, University of Tetovo, Ilinden n.n., 1200 Tetovo, Republic of Macedonia

Published **May 25, 2020**

This Book Chapter is a republication of an article published by Arianit A Reka, et al. at Open Chemistry in December 2019. (Arianit A Reka, Blagoj Pavlovski, Egzon Ademi, Ahmed Jashari, Blazo Boev, Ivan Boev, Petre Makreski. Effect Of Thermal Treatment Of Trepel At Temperature Range 800-1200°C. Open Chemistry, Volume 17, Issue 1, Pages 1235–1243, eISSN 2391-5420, DOI: <https://doi.org/10.1515/chem-2019-0132>.)

**How to cite this book chapter:** Arianit A Reka, Blagoj Pavlovski, Egzon Ademi, Ahmed Jashari, Blazo Boev, Ivan Boev, Petre Makreski. Effect of Thermal Treatment of Clayey Diatomite at Temperature Range 800-1200°C. In: Ayuk Eugene

Lakem, editor. Prime Archives in Chemistry. Hyderabad, India: Vide Leaf. 2020.

© The Author(s) 2020. This article is distributed under the terms of the Creative Commons Attribution 4.0 International License (<http://creativecommons.org/licenses/by/4.0/>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

**Conflict of interest:** Authors declare no conflict of interest.

## Abstract

Trepel is the local name for a mixture of diatomaceous earth and clay minerals. It represents a greyish, soft, very light, weakly cemented, fine biogenetic sedimentary rock. The studied material is taken from the vicinity of Bitola city (Republic of Macedonia). Here, clayey diatomite was treated up to three temperature intervals (800, 1000 and 1200°C) for a period of 1 hour. The X-ray powder diffraction results indicate the presence of both an amorphous phase and the following crystalline phases: quartz, feldspars (plagioclase), mica (muscovite) and chlorites. The results of SEM analysis revealed skeletons of alga Diatomeae with nano-pores. By thermal treatment of the samples, a gradual change in color as well as higher bulk density and compressive strength was observed. The increase of the temperature, in addition, affected the mineralogical composition and increased the presence of the amorphous phase (aluminasilicate glassy phase). SEM results of the thermally investigated samples depicted morphological changes expressed by shrinkage of the pore diameters in comparison to the initial material. The major and minor constituents were established by chemical analysis revealing the following chemical composition of raw clayey diatomite: SiO<sub>2</sub> (63.65 wt%), Al<sub>2</sub>O<sub>3</sub> (11.76 wt%), Fe<sub>2</sub>O<sub>3</sub> (5.93 wt%), MnO (0.13 wt%), TiO<sub>2</sub> (0.63 wt%), CaO (1.42 wt%), MgO (2.22 wt%), P<sub>2</sub>O<sub>5</sub> (0.11 wt%), K<sub>2</sub>O (1.63 wt%), Na<sub>2</sub>O (0.92 wt%), LOI (11.50 wt%).

## Keywords

Clayey Diatomite; Diatomaceous Earth; Clay Minerals; Characterization; Thermal Treatment

## Introduction

Republic of Macedonia is rich in inorganic materials with a wide spectrum of potential use and application [1-4]. Clayey diatomite, found in the vicinity of the Bitola power plant, takes a special place amongst non-metallic materials because it represents a mixture of diatomite and clay minerals [5-14]. It represents a biogenetic rock; grayish, soft, very light, weakly cemented, finely opal sedimentary rock [9]. The results from the physical-chemical and mineralogical-petrographic characterization show that this non-metallic raw material can be used as the basic component in the production of light insulating construction materials, thermal insulators, lightweight construction materials, for the synthesis of zeolites [15], purification of industrial waters [16], in the cement industry (as pozzolanic material) [17- 24] as pesticide holder, as well as for improving the physical and chemical characteristics of certain soils.

According to the physical-chemical and mechanical properties, clayey diatomite is similar to diatomite relying to the compressive strength in natural state, porosity, water absorption, and specific density. Clayey diatomite contains clay minerals (muscovite, chlorites and plagioclase) and its diverse chemical composition makes it an appropriate substance for the production of porous construction and adsorbent material.

The economic effect of using clayey diatomite is based on its fine microstructure and presence of amorphous phase. These properties makes the material highly reactive and utilized as raw product, instead of its treatment as a waste. Therefore, it is used for the production of ceramics at relatively lower temperatures compared to

the classical ceramic raw materials (quartz, feldspars and clay minerals). In addition starting at 1000°C, a mullite is formed as by-product which does not occur when other classical ceramic raw materials are utilized, adding high mechanical properties (compressive strength) of the obtained products.

During the usage of clayey diatomite as a basic material in the industry for production of ceramic materials, of great importance are the mineralogical changes that occur within clayey diatomite during the thermal treatment (i.e. during the sintering process). Due to this fact, the subject of this research paper is the effect of the thermal treatment of clayey diatomite in the temperature interval from 800-1200°C.

## Materials and Methods

The raw material (locally known as trepel), was taken from the Bitola region, Republic of Macedonia.

The chemical composition of raw clayey diatomite was determined with the classical silicate analysis. Crude clayey diatomite was melted in a mixture of carbonates, whereas the percentages of various oxides present in the material are determined with complexometric titration. The alkali metal oxides ( $\text{Na}_2\text{O}$  and  $\text{K}_2\text{O}$ ) were determined with a flame photometry. The determination of the trace elements was performed with Inductively Coupled Plasma Mass Spectrometry (ICP-MS, Agilent 7500cx).

For the purpose of the thermal investigations, raw clayey diatomite was first crushed and ball-milled for a period of 2.5 h. After a powdering procedure of clayey diatomite, 5% of distilled water was added. Then, the mixture was placed in a hermetically closed desiccator for 24 h to achieve the distribution of an even moisture level throughout the mixture. The samples were prepared as cylindrical forms with a diameter of 20 mm and an height of 10 mm under pressure from 2 MPa. Samples were sintered at three temperatures: 800, 1000 and 1200°C for a period of 60 min. The sintered clayey diatomite samples were subjected to compression testing by using an hydraulic press

(Automax 5 – Controls). A minimum of three samples were tested under the same conditions. Upon testing, the material was characterized by physico-mechanical methods. The mineralogical composition was further analysed by XRPD. For each temperature interval, three samples were tested.

The mineralogical characterization of clayey diatomite was carried out by an X-ray powder diffraction (XRPD), thermal analysis (TGA/DTA), scanning electron microscopy (SEM-EDX), transmission electron microscopy (TEM) and infrared spectroscopy (IR).

XRPD analysis was performed on Rigaku Ultima IV X-ray diffractometer equipped with D/teX high-speed 1-dimensional detector using  $\text{CuK}\alpha$  radiation ( $\lambda = 1.54178 \text{ \AA}$ ) in  $2\theta$  range from  $5$  to  $60^\circ$ . The accelerating voltage and the current power were set to  $40 \text{ kV}$  and  $40 \text{ mA}$ , respectively.

DTA/TGA analyses of clayey diatomite were performed in an air environment with Stanton Redcroft apparatus, under the following experimental conditions: temperature range from  $20$ – $1200^\circ\text{C}$ ; speed of heating set to  $10^\circ\text{C}/\text{min}$ ; sample mass of  $13.577 \text{ mg}$ , using ceramic pot as a material carrier.

Scanning electron microscopy VEGA3 LMU coupled with energy dispersive X-ray spectroscopy (INCA Energy 250 Microanalysis System) was used to quantitative analyze the material. The accelerating voltage of the SE detector was set to  $20 \text{ kV}$ .

The Perkin-Elmer FTIR system 2000 interferometer was engaged to record the IR spectra in  $4000$ – $500 \text{ cm}^{-1}$  range using the KBr pellet method. The pellets were prepared by pressing a mixture of the sample and of dried KBr (sample: KBr approximately  $1:200$ ), at  $10 \text{ tons cm}^{-2}$ .

Ethical approval: The conducted research is not related to either human or animal use.

## Results and Discussion

### Physical-Mechanical Properties of Clayey Diatomite

From the physical-mechanical point of view, the examined clayey diatomite subject of this research represents a sedimentary rock (of biogenetic origin) with grayish to grayish-white color, soft (1-2 by Mohs) and very light, with fine to superfine grained structure, porous, shell-like etc. The bulk density of clayey diatomite is  $0.60 - 0.68 \text{ g/cm}^3$ , the density is  $2.41 \text{ g/cm}^3$ , while the compressive strength in natural state (raw) is 3.45 MPa. The physical-mechanical characteristics of clayey diatomite are shown below (Table 1 and Figure 1).



**Figure 1:** Natural (crude) clayey diatomite from Bitola region.

**Table 1:** Physical mechanical properties of raw clayey diatomite.

Bulk density ( $\text{g/cm}^3$ )	0.60–0.68
Water absorption (%)	75–81 %
Open porosity (%)	50–60 %
Total porosity (%)	67–71%
Density ( $\text{g/cm}^3$ )	$2.41 \text{ g/cm}^3$
Compressive strength	3.45 MPa

### Chemical Analysis of Raw Clayey Diatomite

The chemical composition of clayey diatomite (shown on Table 2) is determined with the classical chemical silicate analysis. Crude clayey diatomite was melted in a mixture of carbonates, whereas the percentages of various oxides present in the material were determined with complexometric titration. The alkali metal oxides ( $\text{Na}_2\text{O}$  and  $\text{K}_2\text{O}$ ) were determined with a flame

photometry. The determination of the trace elements was performed with ICP-MS. The loss of ignition (LOI), is determined while heating raw clayey diatomite at 1000 °C for a period of 1 hour was 11.5%. The results obtained from the chemical composition of clayey diatomite indicate that the analyzed material represents an acidic rock with prevailing percentage of SiO<sub>2</sub> (63.65%) and substantial content of Al<sub>2</sub>O<sub>3</sub> and Fe<sub>2</sub>O<sub>3</sub> (11.76% and 5.93). In table 2 and table 3 is shown the chemical composition of oxides and trace elements.

**Table 2:** Chemical composition of clayey diatomite.

Oxides	Mass %
SiO <sub>2</sub>	63.65
Al <sub>2</sub> O <sub>3</sub>	11.76
Fe <sub>2</sub> O <sub>3</sub>	5.93
MnO	0.13
TiO <sub>2</sub>	0.63
CaO	1.49
MgO	2.22
P <sub>2</sub> O <sub>5</sub>	0.11
K <sub>2</sub> O	1.63
Na <sub>2</sub> O	0.92
LOI	11.50
<b>Total</b>	<b>99.99</b>


**Table 3:** Trace elements determined in the naturally occurring clayey diatomite.

Trace element	Content/ppm
Cu	113
Cr	111.2
Ni	40.7
Co	22.7
Zn	3.59
V	112.8
Pb	10.3
Cd	0.060
As	5.9
Se	3.2
Tl	0.97
Bi	0.57
Ba	459.6
Rb	114.2
Sr	166.6

Cs	4.2
Th	9.6
U	7.7
Mo	1.6
Sn	2.8
Sb	0.2
Pd	0.6
Ag	2.5
Ga	16.6
Ge	1.0
Li	32.73
Be	2.6
B	<10

**X-Ray Powder Diffraction Analysis of Raw Clayey Diatomite**

XRPD pattern of clayey diatomite (Figure 2) mainly depicts crystalline behavior with a small presence of amorphous matter. The crystalline phases are mainly represented by silica (quartz peaks at 20.89°, 26.67°, 39.50°, 50.15°, 59.59°), feldspars (plagioclase peaks at 13.89°, 18.84°, 23.58°, 24.32°, 24.66°, 27.82°, 27.95°, 30.24°, 30.52°), mica (muscovite maxima at 8.91°, 17.85°, 19.76°, 26.90°, 29.89°, 31.85°, 34.51°, 38.19°, 42.15°, 45.59°, 45.94°, 52.54°, 55.53°) and chlorites (peaks at 6.26°, 12.53°, 18.84°, 25.20°, 25.53°, 27.82°, 31.28°, 37.41°, 37.65°, 39.50°, 45.59°, 45.94°).

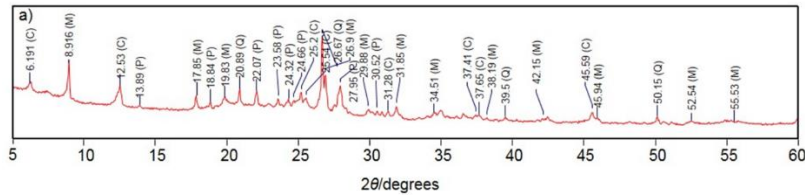


**Figure 2:** XRPD analysis of raw clayey diatomite (Q: quartz, M: muscovite, C: chlorite, P: plagioclase).



## Infrared Spectral Analysis of Raw Clayey Diatomite


The IR spectrum of raw clayey diatomite (Figure 3) exhibits an absorption band at  $797\text{ cm}^{-1}$  attributed to the bending vibrations of Si-O-Si framework, whereas the band at  $1061\text{ cm}^{-1}$  is a result of the stretching vibrations of Si-O-Al units. The band at  $1644\text{ cm}^{-1}$  is due to bending vibrations from the absorbed water, whereas the band at  $3625\text{ cm}^{-1}$  is due to the stretching vibration of the absorbed water molecules [2]. The bands at  $469.9\text{ cm}^{-1}$ ,  $529\text{ cm}^{-1}$  and  $695\text{ cm}^{-1}$  are due to the presence of feldspars in the sample. The bands at  $797\text{ cm}^{-1}$  and  $1080\text{ cm}^{-1}$  are due to the presence of quartz [25, 26].

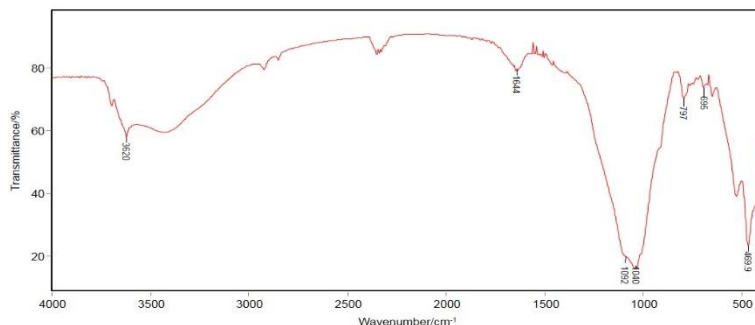


**Figure 3:** IR spectrum of raw clayey diatomite.

## Scanning Electron Microscopy (SEM) of Raw Clayey Diatomite

The results from the SEM of raw clayey diatomite are shown in Figures 4 and 5. The SEM images provide sufficient evidence of the biogenetic nature of the raw material. Various fragments and/or complete skeletal forms of diatoms algae (either in the form of sunflower disks or extended tubes) contain disk or oblong shapes and range from 15 to 60  $\mu\text{m}$ . The observed variations in the shape most likely occur from the clay component in the raw material. SEM morphology of clayey diatomite does not indicate preserved form of the diatom frustules.

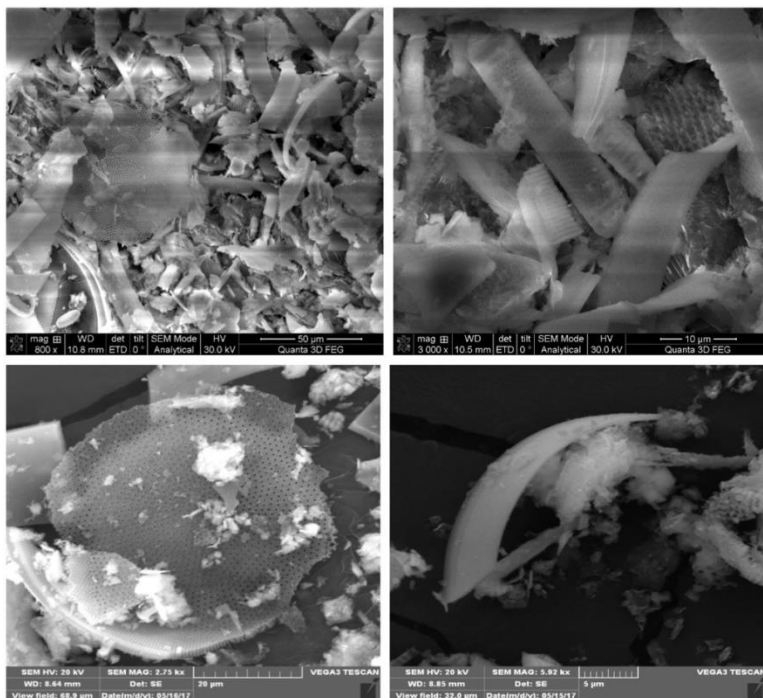

**Figure 4:** SEM pictures of raw clayey diatomite composed of various microreliefs of biogenetic origin with various forms (globular or tubes) with many pores ranging from 350 – 650 nm.

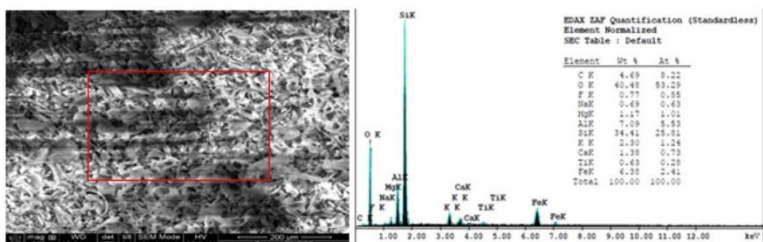


**Figure 5:** SEM-EDX spectrum of raw clayey diatomite.

The EDX spectrum enabled to quantitatively determine the chemical composition. The element weight percentage (C: 4.69%, O: 40.48%, F: 0.77%, Na: 0.69%, Mg: 1.17%, Al: 7.09%, Si: 34.41%, K: 2.30%, Ca: 1.38%, Ti: 0.63%, Fe: 6.38%) confirmed the mixture of diatomaceous earth with the clay minerals.

## Thermal Examinations of Raw Clayey Diatomite

The thermogravimetric analysis (TGA) and the differential thermal analysis (DTA) of the analyzed sample of clayey diatomite is shown in Figure 6. The DTA curve shows a wide endothermic peak with a minimal value of 180°C. This peak is a result of separation of the rough water bonded with the clay minerals and opal component. At the same curve evident is the presence of two exothermic peaks with maximum values of 323°C and 454°C which are result of the burning of organic matter present in clayey diatomite.

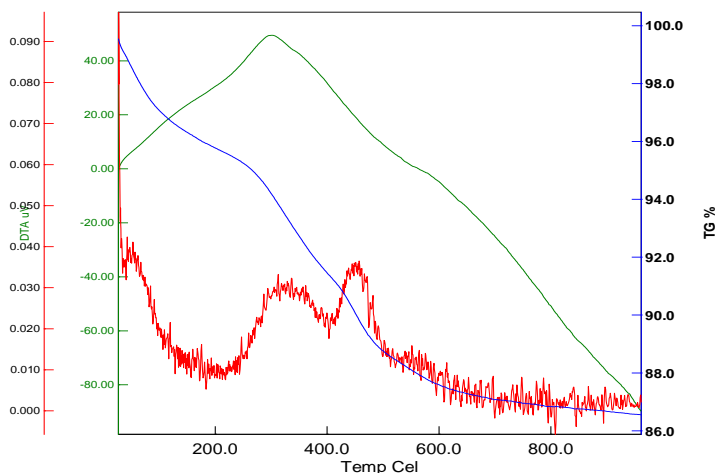


**Figure 6:** DTA/TGA of raw clayey diatomite.

Based on the TGA curve, it is evidence of mass loss during the heating process. The thermogravimetric analysis (TGA) of the analysed clayey diatomite indicates weight loss in three temperature intervals (Figure 6). The first temperature interval ranges between room temperature and 100°C resulting in 2.9% mass loss, attributed to the free water present in the sample. The second temperature interval occurs between 108°C and 600°C with mass loss of 9.55%. This temperature interval is attributed to dehydroxylation of the clay component (muscovite and chlorite) as well as the burning of the present organic matter present in the raw material. The third temperature interval occurs at temperatures higher than 600°C. There, thermogravimetric

curves continually show lower intensity of mass loss (1%) ascribed to the dehydration process of the opal component.

### X-Ray Powder Diffraction Analysis of Thermally Treated Clayey Diatomite Samples

Results of the XRPD analysis of the thermally-induced clayey diatomite at 800°C, 1000°C and 1200°C (Figure 7b–2d) demonstrated crystalline behavior with a small amount of amorphous phase. The crystalline phase is represented mainly by quartz, muscovite, feldspars and chlorites. However, the increase of the temperature expanded the amount of the amorphous phase in the sample. The appearance of the complex positioned “bump” between 15 and 28° (2 $\theta$ ) is attributed to the transformation of the crystalline mass into aluminosilicate glass. During the thermal treatment of clayey diatomite, a slight decrease of the quartz phase was monitored (at 1200°C), but formation of two new phases was evidenced – mullite (maxima at 16.33°, 25.86°, 26.19°, 33.29°, 35.07°, 40.65°, 40.98°, 42.40°, 54.33°) and tridymite (maxima at 20.80°, 21.63°, 24.23°, 32.65°, 35.71°, 44.30°).

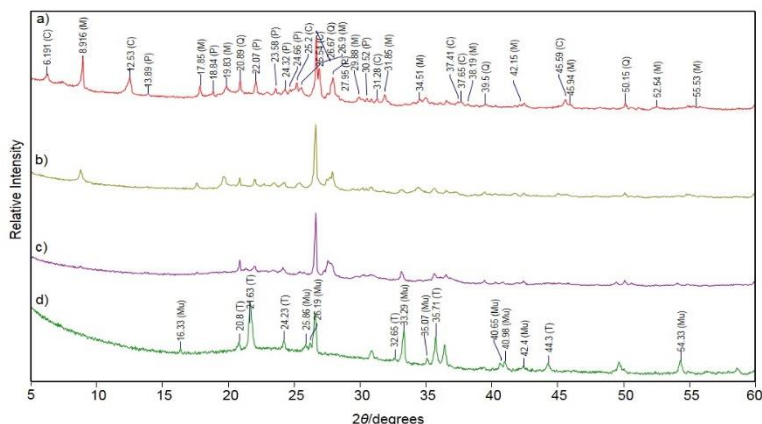

**Figure 7:** XRPD analysis of raw clayey diatomite (a), and thermally treated sample for a period of 1 hour at 800°C for a period of 1 hour, (b) at 1000°C for a period of 1 hour, (c) and at 1200°C for a period of 1 hour (d).

## Shrinkage of the Samples after Compressing and Heat Treatment

Physico-mechanical features of the thermally treated samples (Figure 8) indicate gradual change in colour from ochre to black as the temperature increases, accompanied by a gradual increase of the bulk density and abrupt rise of the compressive strength (Table 4). In addition, a diameter of the pellets as well as the mass of the samples decreased with ramping the temperature to 800, 1000 and 1200°C. The shrinkage of the diameter ranges from 0.8% at 800°C to 8.7% at 1200°C



**Figure 8:** Shrinkage and the obvious change in color of cylinders of clayey diatomite sintered at 800, 1000 and 1200°C for a period of 60 min.


**Table 4:** Physical-mechanical properties of cylinders of raw clayey diatomite compared to the sintered samples at 800, 1000 and 1200°C for a period of 60 min.

Temperature (°C)	Bulk density (g/cm <sup>3</sup> )	Compressive strength (MPa)	Mass (g)	Diameter (mm)	Shrinkage (%)
800	0.81	4.40	2.25	19.84	0.80
1000	0.94	14.94	2.17	19.25	3.75
1200	1.30	32.48	2.11	18.26	8.70

The thermal treatment of the samples shows evidence of mineralogical composition changes and amorphous fraction increase.

## SEM of Thermally Treated Clayey Diatomite

The SEM results of the SE micrographs of the thermally treated samples provided important knowledge (Figure 9) in regards to the morphological changes occurring during the sintering process. Namely, the pores of the various skeletal forms were reduced from the 350– 650 nm to 150–250 nm that is particularly important that can be exploited for the further use and application of the raw material as a filtration source.

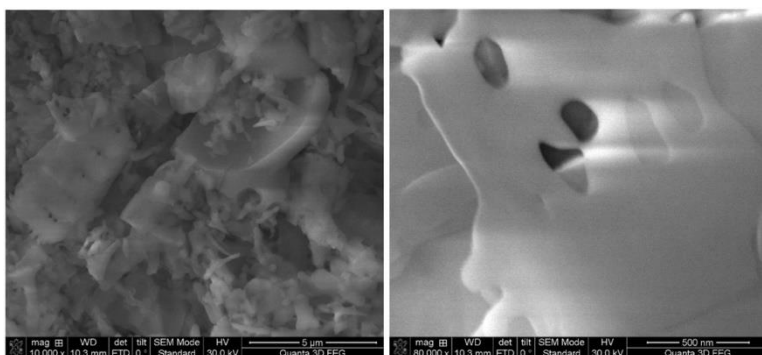

**Figure 9:** SEM of thermally treated sample.

## Conclusions

From the physical-mechanical point of view, clayey diatomite represents a porous sedimentary rock (of biogenetic origin) with grayish to grayish-white color, soft and very light, with fine to superfine grained structure. The bulk density of clayey diatomite is 0.60 – 0.68 g/cm<sup>3</sup>, the density amounts 2.41 g/cm<sup>3</sup>, the compressive strength in natural state (raw) is 3.45 MPa, while the total porosity is from 67-71%. According to the chemical composition, it can be concluded that clayey diatomite represents acidic rock with a dominant presence of silica at 63.51%. The mineralogical characterization revealed the presence of the following minerals: quartz, plagioclase, muscovite and chlorite. Maintaining the 800°C temperature for a period of 1 hour significantly decomposed the present feldspars. The thermal

treatment at 1000°C results in the formation of mullite, which is unusual to form at this temperature. However, its appearance is prescribed to the high reactivity of clayey diatomite (the super fine particles and the presence of the amorphous phase). Further temperature increase up to 1200°C, majorly increased the mullite phase with simultaneous increase of the amorphous phase followed with the appearance of tridymite.

SEM shows globular forms of quartz, skeletons from diatomae algae and other forms of clay minerals; whereas the thermally treated samples show morphological changes followed by the decrease of the size of the pores in the raw material. The reduction of the pores makes this materials suitable for filtration purposes.

Based on the abovementioned results, it can be concluded that at significantly lower temperatures, due to the appearance of mullite as binding component which enables high mechanical properties, clayey diatomite can be used as basic raw material for obtaining various types of ceramic materials (construction materials and various thermal insulating materials), various types of zeolites, waterglass, amorphous SiO<sub>2</sub> etc.

## References

1. Spasovski O, Spasovski D. The potential of the nonmetallic mineral resources in the Republic of Macedonia. *Geologica Macedonica*. 2012; 26: 91-94.
2. Makreski P, Jovanovski G, Kaitner B. Minerals from Macedonia. XXIV. Spectra-structure characterization of tectosilicates. *J. Mol. Struct.* 2009; 924-926: 413-419.
3. Jovanovski G, Boev B, Makreski P. Minerals from the Republic of Macedonia with an Introduction to Mineralogy. *Macedonian Academy of Sciences and Arts, Skopje*. 2012; 1–652.
4. Reka AA, Pavlovski B, Lisichkov K, Jashari A, Boev B, et al. Chemical, mineralogical and structural features of native and expanded perlite from Macedonia. *Geologia croatica*. 2019; 72: 215-221.

5. Pavlovski B, Zafirovski S, Zlatanovic V. Lightweight ceramic construction materials with hydrosilicate bonding. Proceedings of the VII Yugoslavian Congress for Chemistry and Technology. Novi Sad, Yugoslavia. 1983; 77-81.
6. Pavlovski B, Buntevska V. Lightweight ceramic materials obtained by hydrothermal procedure. Book of Abstracts of the XVI Congress of Chemists and Technologists of Macedonia. Skopje, Macedonia. 1999; 96.
7. Reka A. Influence of mineralogical composition and microstructure of the binding material on the physico-mechanical properties of ceramic products obtained by hydrothermal process, PhD thesis. Ss. Cyril and Methodius University. Skopje, Macedonia. 2004.
8. Reka A, Pavlovski B. Influence of the nature of silica on physical and mechanical properties of lightweight silicate bonded building products obtained by hydrothermal treatment. Book of Abstracts of the XVIII Congress of Chemists and Technologists of Macedonia. Ohrid, Macedonia. 2004; 78.
9. Pavlovski B, Jančev S, Petreski L, Reka A, Bogoevski S, et al. Trepel – a peculiar sedimentary rock of biogenetic origin from the Suvodol village, Bitola, R. Macedonia. *Geologica Macedonica*. 2011; 25: 67-72.
10. Cekova B, Pavlovski B, Spasev D, Reka A. Structural examinations of natural raw materials pumice and trepel from Republic of Macedonia. Proceedings of the XV Balkan Mineral Processing Congress. Sozopol, Bulgaria. 2013; 73-75.
11. Reka AA. Synthesis and characterization of porous SiO<sub>2</sub> ceramics obtained from diatomite with the use of low-temperature hydrothermal technology, PhD thesis. Ss. Cyril and Methodius University. Skopje, Macedonia. 2016.
12. Reka AA, Pavlovski B, Makreski P. New optimized method for low-temperature hydrothermal production of porous ceramics using diatomaceous earth. *Ceram. Int.* 2017; 43: 12572-12578.
13. Reka AA, Anovski T, Bogoevski S, Pavlovski B, Boškovski B. Physical-chemical and mineralogical-petrographic examinations of diatomite from deposit near village of



- Rožden, Republic of Macedonia. *Geologica Macedonica*. 2014; 28: 121-126.
14. Reka AA, Pavlovski B, Anovski T, Bogoevski S, Boškovski B. Phase transformations of amorphous SiO<sub>2</sub> in diatomite at temperature range of 1000–1200°C. *Geologica Macedonica*. 2015; 29: 87-92.
  15. Cekova B, Pavlovski B, Spasev D. Examining the possible use of natural raw material “Trepel” - Bitola for the synthesis of zeolite type 4A. *Book of Abstracts of the XXII Congress of Chemists and Technologists of Macedonia*. Ohrid, Macedonia. 2012; 222.
  16. Memedi H, Atkovska K, Lisichkov K, Marinkovski M, Kuvendziev S, et al. Removal of Cr(VI) from water resources by using different raw inorganic sorbents. *Quality of life*. 2016; 7: 77-85.
  17. Fragoulis D, Stamatakis MG, Papageorgiou D, Chaniotakis E. The physical and mechanical properties of composite cements manufactured with calcareous and clayey Greek diatomite mixtures. *Cement Concrete Comp*. 2005; 27: 205-209.
  18. Rahimov RZ, Kamalova ZA, Ermilova EJO, Stojanov V. Thermally treated trepel as active mineral additive in cement. *Gazette of Kazan Institute of Technology*. 2014; 17: 99-101.
  19. Ilia IK, Stamatakis MG, Perraki TS. Mineralogy and technical properties of clayey diatomites from north and central Greece. *Cent. Eur. J. Geosci*. 2009; 1: 393-403.
  20. Ibrahim SS, Selim AQ. Heat treatment of natural diatomite. *Physicochem. Probl. Miner. Process*. 2012; 48: 413-424.
  21. Akhtar F, Rehman Y, Bergström L. A study of the sintering of diatomaceous earth to produce porous ceramic monoliths with bimodal porosity and high strength. *Powder Technol*. 2010; 201: 253-257.
  22. Loganina VI, Simonov EE, Jezierski W, Małaszkievicz D. Application of activated diatomite for dry lime mixes. *Constr. Build. Mater*. 2014; 65: 29-37.
  23. Zheng R, Ren Z, Gao H, Zhang A, Bian Z. Effects of calcination on silica phase transition in diatomite. *J. Alloys Comp*. 2018; 757: 364-371.

24. Paules D, Hamida S, Lasheras RJ, Escudero M, Benouali D, et al. Characterization of natural and treated diatomite by laser-induced breakdown spectroscopy (LIBS). *Microchem. J.* 2018; 137: 1-7.
25. Makreski P, Jovanovski G. Minerals from Macedonia. IX. Distinction between some Rhombohedral Carbonates by FTIR Spectroscopy. *Bull. Chem. Technol. Macedonia.* 2003; 22: 25-32.
26. Šontevska V, Jovanovski G, Makreski P. Minerals from Macedonia. XIX. Vibrational spectra of some sheet silicate minerals. *J. Mol. Struct.* 2007; 834-836: 318-327.